

Experimental Investigation on Process Parameters for Optimization of Surface Roughness and Material Removal Rate in Plano Miller Machine on Carbon Steel IS-2062 Material

H. S. Patil

Professor, Mechanical Department, GIDC Engineering College, Abrama, Navsari, Gujarat, India.

D. C. Patel,

Associate Professor, Mechanical Department, GIDC Engineering College, Abrama, Navsari, Gujarat, India.

C. S. Patil

Asst. Professor, Mechanical Department, S. S. Agrawal Institute of Engg. & Technology, Navsari, Gujarat, India.

Abstract – In the present work, the parametric optimization method using Taguchi's robust design is proposed for Plano miller machining of carbon steel IS-2062 with coated cemented tungsten carbide tip tool. In this paper, the effects of process parameters like cutting speed, feed rate and depth of cut have been investigated to reveal their impact on material removal rate and surface roughness. Experiments runs on plano miller machine based on Taguchi's L9 orthogonal array were performed; signal to noise (S/N) ratios, and analysis of variance (ANOVA) were used to optimize the material removal rate and minimum surface roughness. From the optimization and experimental analyses conducted, it was observed that process parameters had significant influence in obtaining a better surface integrity. The optimal values obtained during the study optimization by Taguchi approach was validated by confirmation experiments. Optimum value of the surface roughness (Ra) and material removal rate (MRR) comes out to be 1.92 μm and 13.24x10⁻⁶ mm³/min respectively.

Index Terms – Plano Milling; Process parameter, Taguchi's method; Carbon steel IS-2062

1. INTRODUCTION

In engineering industries, machining is a major manufacturing process. Product performance to a large extent is dependent on the precision and consistency of the machining processes used to produce the parts. Cutting parameters in machining-speed, feed and depth of cut are to be the maximum to reduce the product cycle time. These cutting parameters are dependent on machine tools, work-holding, cutting tool materials and their capability to withstand the generation of heat and shock loads during the cutting, tool rigidity, and coolant. Plano miller machine is type of metalworking machine tools that uses linear as well as rotational relative motion between the work piece and a milling cutter to cut the

work piece. A Plano Miller is similar to a planer & milling machine but in this machine, cutting tool has rotary motion and it is fixed at its fix position and table with work piece moving towards it.

In order to produce parts of desired quality, proper machining parameters like spindle speed, feed rate, depth of cut, cutter diameter, number of cutting flutes, and tool geometry must be selected. Design of experiments (DOE) is a systematic, approach to engineering problem-solving that applies principles and techniques at the data collection stage to ensure the generation of valid and supportable engineering conclusions. Also all of this is carried out under the constraint of a minimal expenditure of engineering runs, time, and money. Taguchi method which is a technique of Design of experiments can be used for attaining high quality at minimum cost. The quality obtained by means of the optimization of the product or process is found to be cost effective [1]. Response surface methodology (RSM) which is another analysis technique is a collection of mathematical and statistical techniques for empirical model building where the objective is to optimize a response (output variable) which is influenced by several independent variables (input variables) [2]. Al-Refaie et al. used Taguchi method coupled grey analysis to determine the optimal combination of control parameters in milling, the measures of machining performance being the MRR and SR [3]. Benardos et al studied prediction of surface roughness in CNC face milling using neural networks and taguchi's DOE and concluded that roughness has been significantly influenced by feed rate, speed and depth of cut [4]. A systematic approach for identifying optimum surface roughness performance in end milling operations has been presented by Taguchi parameter

design at the minimum cost [5]. Kumar et al. optimized turning parameters based on the Taguchi's method with regression analysis. They developed model for prediction of surface roughness and material removal rate in machining of unidirectional glass fiber reinforced plastics composites with a polycrystalline diamond tool [6]. Mustafa et al. investigated the effect of feed rate, cutting speed and depth of cut on surface roughness, cutting temperature and cutting force in turning of aluminium 7075 alloy using diamond like carbon coated cutting tools [7]. Aruna et al. developed a model for predicting the surface roughness based on cutting speed, feed and depth of cut using response surface methodology. Surface roughness contour for cutting speed-depth of cut is developed to describe the values resulting from the cutting parameters selected [8]. Feed rate was the most significant machining parameter used to predict the surface roughness in the multiple regression models [9]. Suresh et al. developed a mathematical model for predicting value of surface roughness while machining mild steel using response surface methodology and optimized the developed model using genetic algorithm, in order to attain the required surface quality [10]. RSM can be utilized to create an efficient analytical model for surface roughness in terms of cutting parameters: feed, cutting speed, axial depth of cut, radial depth of cut and machining tolerance [11]. Surface roughness of machined work piece depends on technological parameters (cutting speed; feed; cutting depth) and concluded that technological parameter range also plays a very important role on surface roughness [12]. The various literature reviewed here indicated that different researchers were tried to optimize various machining processes for improving the quality of the product. Among different quality attributes surface finish of the component obtained after various machining processes is considered to be most important. This paper presents the optimization of machining parameters like cutting speed; feed rate and depth of cut for surface roughness and material removal rate for carbon steel 2060 material using plano miller.

2. MATERIAL AND EXPERIMENTAL METHODS

In experimental analysis the old planer machine has been converted in plano miller machine in EM tech Fabrication–small scale unit located in our Navsari industrial region with our support. Experimental works were carried out on converted plano miller machine as in figure 1. In a converted plano miller mechanical table drive units (MTDU) is the most economical solution for the table feed system. In a converted plano miller the MTDU consists of a reconditioned 5-speed Gear Box of Fiat car and 1 HP DC motor is used to run the drive. AC Motor of 7 HP was installed in tool head for spindle rotation. The tool holder has rotational motion and it is fitted with bearing housing. Four tools can be fitted in tool holder at a time for machining operation. These tools can be adjusted with the different heights.



Figure 1 Converted plano miller machine with gear box

Carbon steel 2062 was used as work piece material of dimension 150mm x 100 mmx15mm. The chemical composition of workpiece material is shown in Table 1.

Table 1 Chemical properties of carbon steel IS-2062

Elements	Composition (Wt. %) Max
C	0.23
Mn	1.5
S	0.05
P	0.05
Si	0.4
C.E.	0.42

The carbide tip single point cutting tool is used for matching process at various parameters. The tool size is 20cmx5cmx5cm. Cutting Tool Holder and single point carbide tip tool is shown in figure 2.



Figure 2 Cutting Tool Holder and single point carbide tip tool

Experimental analysis has been carried out based on standardized DOE of L9 Taguchi orthogonal array of experiments to optimize the processing parameters. Roughness and material removal rate in plano miller process

analyzed properly based on the preliminary trials on selected independent process parameters as shown in Table 2 that affects the surface finish and material removal rate. In this study, spindle speed, feed rate and depth of cut were considered as machining parameters.

In order to eliminate any surface defects and wobbling, Work pieces were cleaned prior to the experiments by removing 0.3 mm thickness of the top surface. Material removal rate was calculated by using equation. The average surface roughness (Ra) was measured after machining, in the feed direction using a hand held roughness tester TR200. The optimal results were verified with the help of analysis of variance (ANOVA).

Independent process parameters that affect the surface finish and material removal rate were identified as spindle speed, feed rate, depth of cut. Alloy Steel material, is machined with DOE set of trials using its ranges of operation as per the recommendations EM Tech Fabrication, Navsari.

Table 2 Machining process parameters and their levels

Factors	Level 1	Level 2	Level 3
Cutting Speed	250	300	400
Feed Rate	0.63	0.71	1.42
Depth of cut	0.5	1	1.5

3. RESULTS AND DISCUSSIONS

3.1 Effect of process parameters on the Surface Roughness

Experiments were conducted using L9 orthogonal array in order to understand the effect of process parameters on the surface roughness and material removal rate and the obtained results are shown in Table 3 and 4. The average experimental values of surface roughness for each parameter at levels 1, 2 and 3 for signal-to-noise (S/N) ratios are plotted in Table-3.

Table 3 Experimental results of surface roughness and S/N ratios

Ex. No.	Spindle speed (rpm),	Feed Rate (mm/rev)	Depth Of Cut (mm)	Surface Roughness (µm)	S-N Ratio of SR
1.	250	0.63	0.5	8.2	18.27
2.	250	0.71	1	2.35	7.42
3.	250	1.42	1.5	1.92	5.66
4.	300	0.63	0.5	10.36	20.30
5.	300	0.71	1	8.11	18.18
6.	300	1.42	1.5	10.67	20.56
7.	400	0.63	0.5	10.80	20.66

8.	400	0.71	1	8.25	18.32
9.	400	1.42	1.5	2.61	8.33

The main effect plots of S/N ratios on surface roughness (Ra) are plotted graphically using MINITAB software as shown in figure.3. The figures specify the influence of process parameters on the surface roughness and it has been observed that roughness value increases with increase in cutting speed and decreases as the feed rate and depth of cut increases. The almost equivalent influence was observed on surface roughness experimentally as per figure 4 with respect to parameters. The experimental results showed that the optimal combination of parameters for surface roughness are at cutting speed of 250 rpm, feed rate of 1.42 mm/rev, depth of cut of 1.5 mm with optimum value of the surface roughness (Ra) comes out to be 1.92 µm lower than other combinations

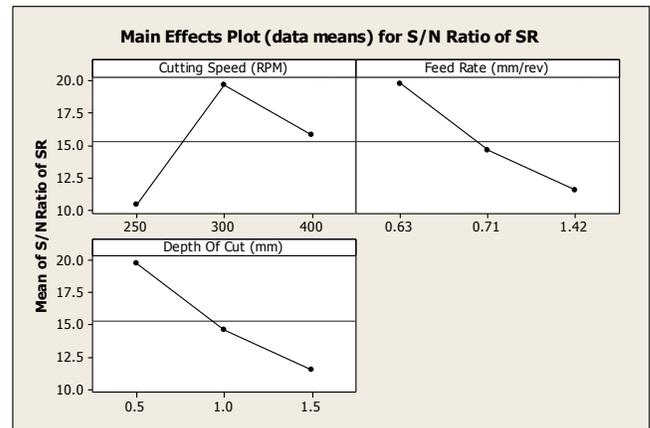


Figure 3 Main effects plot for S/N ratios for surface roughness

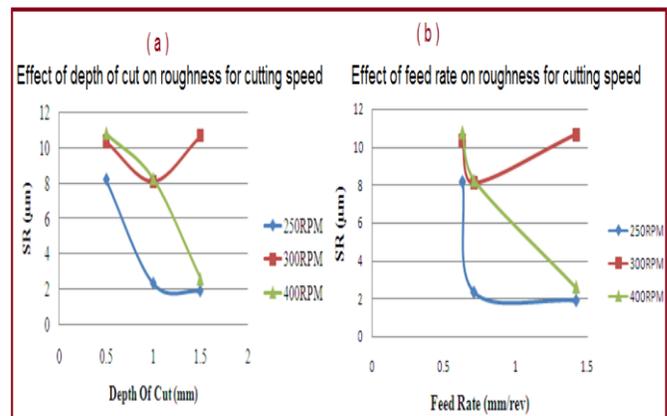


Figure 4 Effect of depth of cut and feed rate on surface roughness for various cutting Speeds

3.2 Effect of process parameters on the material removal rate

The average experimental values of material removal rate for each parameter at levels 1, 2 and 3 for signal-to-noise (S/N) ratios are plotted in Table-4.

Table 4 Material removal rate and S/N Ratio of MRR

Ex. No.	Spindle speed (rpm)	Feed Rate (mm/rev)	Depth of Cut (mm)	MRR (mm ³ /min)	S/N Ratio of MRR
1.	250	0.63	0.5	4.07*10 ⁻⁶	-107.80
2.	250	0.71	1	4.53*10 ⁻⁶	-106.88
3.	250	1.42	1.5	4.14*10 ⁻⁶	-107.65
4.	300	0.63	0.5	2.15*10 ⁻⁶	-113.35
5.	300	0.71	1	3.14*10 ⁻⁶	-110.06
6.	300	1.42	1.5	5.36*10 ⁻⁶	-105.34
7.	400	0.63	0.5	6.72*10 ⁻⁶	-103.45
8.	400	0.71	1	6.25*10 ⁻⁶	-104.08
9.	400	1.42	1.5	13.24*10 ⁻⁶	-97.56

The main effect plots of S/N ratios on material removal rate MRR are plotted graphically using MINITAB software as shown in figure 5. It has been observed that MRR increases with increase in cutting speed, feed rate and depth of cut. Cutting theory state that material removal rate is directly proportional to the spindle speed, feed rate and depth of cut. The spindle speed refers the speed at which the work piece material is moving past the cutting tool. Feed always refers to the cutting tool, and is the rate at which the tool advances along its cutting path. The feed rate is directly related to the spindle speed.

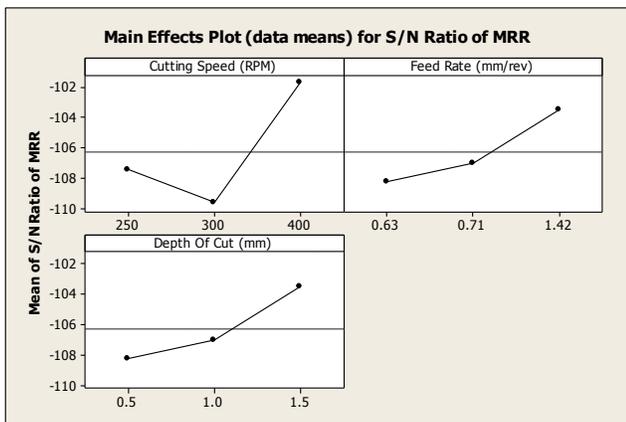


Figure 5 Main effects plot for S/N ratios for material removal rate (MRR)

Thus, as spindle speed increases the feed rate too increases, thereby resulting in increase in material removal rate. Depth of cut is the thickness of the layer being removed (in a single pass) from the work piece or the distance from the uncut surface of the work to the cut surface. Thus, the volume of

material removed increases with increase in depth of cut. The almost equivalent effect was observed on removal rate experimentally as per figure 6 except at cutting speed 400rpm.

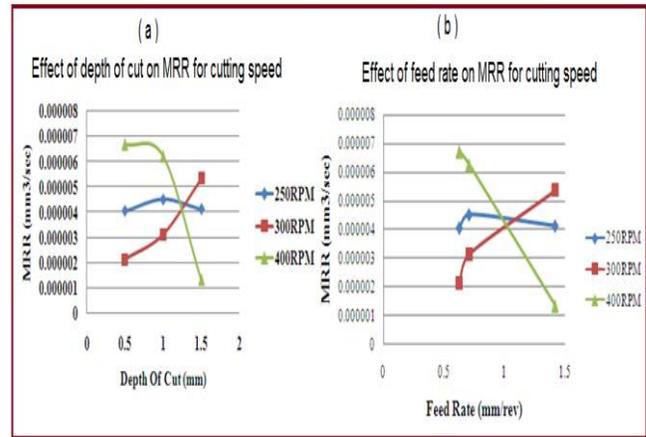


Figure 6 Effect of depth of cut and feed rate on removal rate for various cutting speed

3.3 Analysis of variance (ANOVA) for surface roughness and material removal rate

ANOVA is a standard statistical technique to interpret experimental outcomes and used to detect differences in average performance of groups of items under investigation. It breaks down the variation in the experimental result into liable sources and thus finds the parameters whose contribution to total variation is significant. Thus ANOVA is used to study the relative influences of multiple variables, and their significance. The purpose of ANOVA is to investigate which process parameters significantly affect the quality characteristic. The analysis of the experimental data is carried out using the software MINITAB 14 specially used for DOE applications. In order to find out statistical significance of various factors like speed, feed, and depth of cut, and their interactions on SR and MRR, analysis of variance is performed on experimental data. Table 5 and 6 shows the result of the ANOVA with the roughness and removal rate.

Table 5 Analysis of variance for means of surface roughness

Source	DOF	Seq SS	Adj MS	F	P
Cutting Speed	2	46.47	23.23	-5.27	0.4219
Feed rate	2	36.24	18.12	-4.11	0.3290
Depth Of Cut	2	36.24	18.12	-4.11	0.3290
Error	2	-8.82	-4.41		
Total	8				
S = 110.13					

Table 6 Analysis of variance for means of material rate

Source	D O F	Seq SS	Adj MS	F	P
Cutting Speed	2	4.69*10 ⁻¹¹	2.34*10 ⁻¹¹	-0.085	0.0558
Feed rate	2	2.91*10 ⁻¹⁰	1.45*10 ⁻¹¹	-0.053	0.346
Depth of Cut	2	2.91*10 ⁻¹⁰	1.45*10 ⁻¹¹	-0.053	0.346
Error	2	-5.46*10 ⁻¹⁰	-2.73*10 ⁻¹¹		
Total	8				
S = 0.84*10⁻¹⁰					

The F value calculated through MINITAB software is shown in the second last column of ANOVA table which suggests the significance of the factors on the desired characteristics. Larger is the F value higher is the significance (considering confidence level of 95%). It can be seen from this table that for the surface finish (Ra), the contribution of cutting speed (42.19%) is more significant than feed rate and depth of cut. Similarly for the MRR, the contribution of feed rate and depth of cut (34.60%) are more significant than cutting speed. It is clear that the effect of noise factor on MRR is very low as compared to the control factors.

4. CONCLUSIONS

The experimental results showed that the optimal machining parameters for surface roughness are at cutting speed of 250 rpm, feed rate of 1.42 mm/rev, depth of cut of 1.5 mm. Optimum value of the surface roughness (Ra) comes out to be 1.92 μ m. The percentage error between experimental and predicted result is 8 % for roughness. Similarly for material removal rate optimal machining parameters are at cutting speed of 400 rpm, feed rate of 1.42 mm/rev, depth of cut of 1.5 mm for the material IS-2062. Optimum value of the material removal rate (MRR) comes out to be 13.24x10⁻⁶ mm³/min. The percentage error between experimental and predicted result is 6.5 % for removal rate. The surface roughness is mainly affected by cutting speed, feed rate & depth of cut. With the increase in feed rate & depth of cut the surface roughness decreases, as the cutting speed increases the surface roughness first increase and decrease. From ANOVA analysis, it has been observed that cutting speed has significant effect on surface roughness while feed rate and depth of cut have significant effect on material removal rate.

REFERENCES

- [1] Taguchi G, Konishi S "Taguchi, Methods, orthogonal arrays and linear graphs, tools for quality" American supplier institute, American Supplier Institute; 1987 [p. 8-35]
- [2] George E. P. Box and Norman R. Draper , "Response Surfaces, Mixtures, and Ridge Analyses", Published Online Wiley Series in Probability and Statistics 10 APR 2006

- [3] A. Al-Refaie, L. Al-Durgham, N. Bata, "Optimal parameter design by regression technique and grey relational analysis", The World Congress of Engineering, pp. 35-42, 2010.
- [4] Benardos., Vosniakos., "Prediction of Surface Roughness in CNC Face Milling Using Neural Networks and Taguchi's Design of Experiments", Robotics And Computer-Integrated Manufacturing, 18(5-6), 343-354.
- [5] Yang.J.L.,Chen.J.C., "A Systematic Approach For Identifying Optimum Surface Roughness Performance In End- Milling Operations" Journal Of Industrial Technology, Volume 17, Number 2-5.
- [6] S. Kumar, M. Gupta, P.S. Satsangi, H.K. Sardana, "Modeling and analysis for surface roughness and material removal rate in machining of UD-GFRP using PCD tool", International Journal of Engineering, Science and Technology, Vol. 2(8), 2010, pp. 248-270.
- [7] A. Mustafa, K. Tanju , "Investigation of the machinability of the Al 7075 alloy using DLC coated cutting tools", Science Research and Essay, Vol. 6(1), 2011, pp. 44-51.
- [8] M. Aruna, V. Dhanalaksmi, "Design optimization of cutting parameters when turning Inconel 718 with cermet inserts", World Academy of Science, Engineering & Technology, Vol. 61, 2012 pp.952-955
- [9] Lou.M.S., Chen.J.C. , Caleb.M., "Surface Roughness Prediction Technique for CNC End-Milling", Journal of Industrial Technology, Volume 15, Number 1-6.
- [10] P.V.S. Suresh, P. V. Rao, S.G. Deshmukh , "A genetic algorithmic approach for optimization of surface roughness prediction model", International Journal of Machine Tool and Manufacture, Vol. 42, 2002, pp. 675-680.
- [11] Oktem.H., Kurtaran.H., "Application of response surface methodology in the optimization of cutting conditions for surface roughness", Journal of Material Processing Technology 170, Pp. 11–16.
- [12] Kromanis.A., Krizbergs., "Surface Roughness Prediction Technique In End Milling Using Regression Analysis", Tallinn, Estonia Industrial Engineering, pp. 42-51.2008

Authors



Dr. H. S. Patil, currently working Professor and Head in Mechanical Department, GIDC Degree Engineering College, Abrama, Navsari, affiliated to Gujarat Technological University Ahmedabad, Gujarat, India. He received a M. E. and Ph.D. degree in Mechanical Engineering from S.V. Regional Engineering College and Veer Narmad South Gujarat University, Surat (India) respectively. His research interest includes design and manufacturing, materials characterization and weld Joint design by FSW and so on.



D. C. PATEL received a M. Tech. degree and Ph.D. degree in Mechanical Engineering from S.V. N. I. T., Surat (India) respectively. Currently working as Associate Professor, Mechanical Department, GIDC Engineering College, Abrama, Navsari, affiliated with Gujarat Technological University Ahmedabad, Gujarat, India. His research interests include Design and Manufacturing, Materials and so on.



C. S. PATIL working as Assistant Professor, Mechanical Department, S. S. Agrawal Institute of Engineering and Technology, Navsari ,Gujarat, India. He received a B. E. and M.E. degree in Mechanical Engineering from D.N.Patel Engineering College, Shahada affiliated to North Maharashtra University Jalgaon, (India). His research area include design and manufacturing,